

IGP-HWF 3001

Sustainable facade protection
by a high weather resistant
powder coating



With the innovative
IGP-DURA[®]clean effect



Powderful Solutions.

IGP-HWF 3001 – highly weather-resistant facade protection for lasting aesthetic appeal

High performance for high levels of pollution

The functionality, elegance and aesthetic appeal of a facade are very short-lived without protection and maintenance. This applies particularly to facade designs subjected to high levels of pollution. High levels of sunshine, extreme variations in climate and caustic pollutant emissions can all have a considerable effect on aesthetically appealing facades.

The IGP-HWF 3001 powder coating system was developed especially to comprehensively protect painted surfaces against unfavourable weather conditions and environmental influences. Thanks to minimal adherence of dirt and a high level of gloss and color stability, your building's envelope will remain protected for a long time to come.

Excellent weathering stability




Compared with standard facade powder coatings, IGP-HWF 3001 has three times the weathering stability. This protects your facade against chalking and color changes.

In addition to RAL and NCS colors, our lab team will also help you to realise your own individual color ideas, and match them with the high requirements in terms of weather-resistance. The product quality we offer, meets the GSB "Master" and/or Qualicoat "Class 2" standards.

IGP-DURA[®]clean effect for reduced dirt adhesion



Both weathering and surface cleaning leave traces on facades over time. Why not put your trust in the unique protection offered by IGP-DURA[®]clean. It repels dirt and is resistant to weathering and cleaning. As a result, cleaning intervals can be extended, saving maintenance costs. The environment benefits too, because excellent cleaning results can be achieved with just a little water and a sponge – with no cleaning agents required.

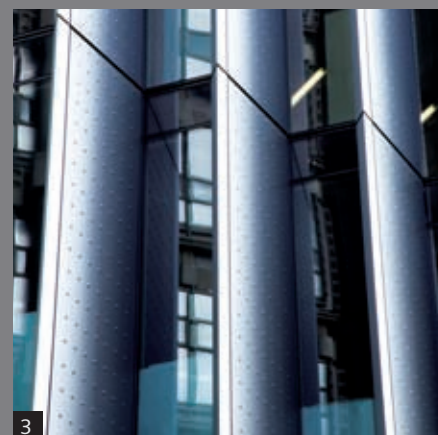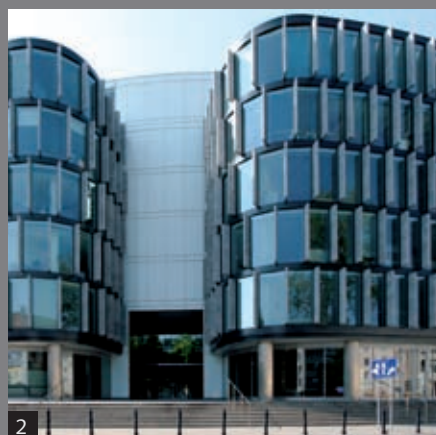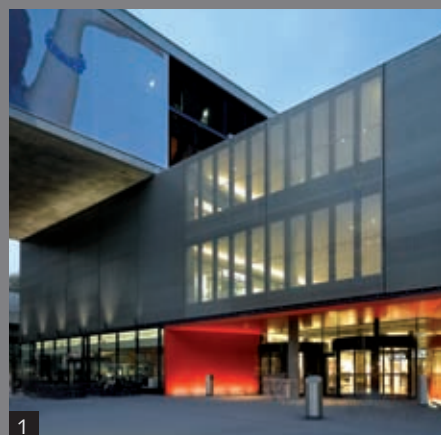

Captions

Jakobsturm, Basel (front page)

Sihlcity, Zurich (1)

Metropol, Warsaw (2)

The Willis Building, London (3)

Consistently high color and gloss durability confirmed in weathering and long-term tests

Available colors

IGP-HWF 3001 is available in an extended range of HWF colors with various gloss levels, in plain colors, in mica and with metallic effects, and as a transparent powder coating.

- RAL and NCS-S colors
- Pearl mica colors
- Mica iron oxide effects
- Various colors developed from samples

Optimised ageing

A special bonding agent system protects the surface against chalking, and UV-resistant pigments provide improved color retention.

The IGP-DURA[®]clean effect makes the coated surface even more water-repellent, thus guaranteeing minimal dirt adhesion, effectively preventing build-ups of residual dirt and particle residues. The surface displays what it is supposed to display, and for longer.

Florida weathering

Whereas standard facade powder coatings may exhibit major gloss and color differences from the initial sample, the weathering values of IGP-HWF 3001 remain constant over a period three times as the Florida weathering test.

The Florida time values correspond to between three and four times the exposure period in a central European climate.

WOM weathering




The highly weather-resistant IGP-HWF 3001 system has enhanced the positive properties of conventional powder coatings. Its improved weathering properties are also demonstrated in the accelerated weathering in the Weather-O-Meter[®] (WOM) test.

IGP-HWF 3001 product range

Surface aspect qualities	
IGP-HWF 3001 5909	gloss
IGP-HWF 3001 5907	silk gloss
IGP-HWF 3001 5903	matt
IGP-HWF 3001 591M	fine texture, matt

The surfaces are available in a smooth flow variation as well as in the fine structure 591M

Color change RAL 5010 – 700-hour QUV-B, DIN 53384

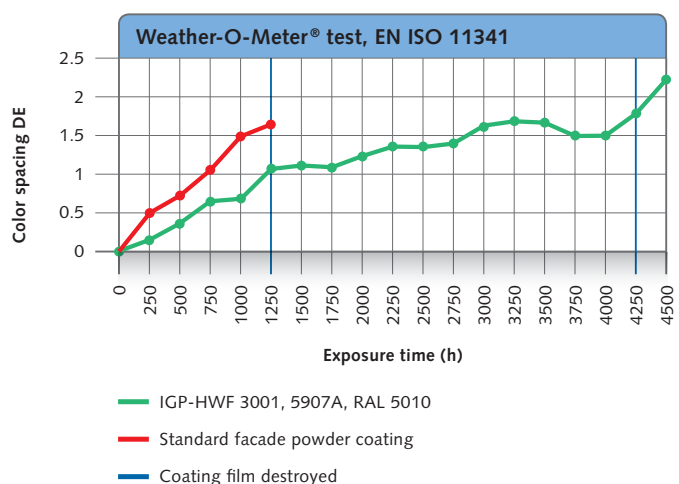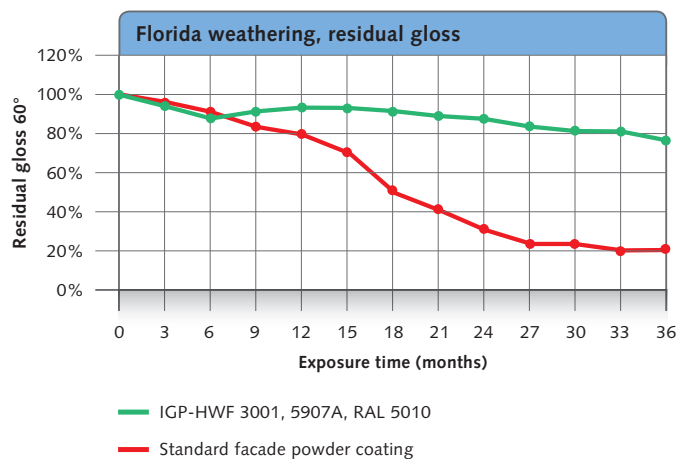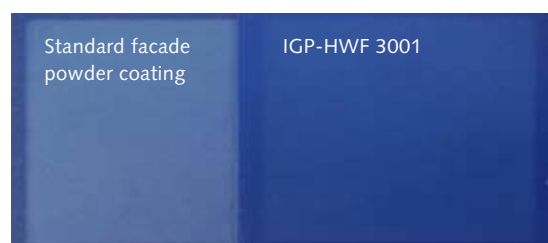

IGP-HWF 3001 – at a glance

Application	Product series	Target values
Object temperatures	5909/5907/591M	20 – 30 Min. 180 °C 15 – 25 Min. 190 °C 10 – 20 Min. 200 °C
	5903	15 – 25 Min. 190 °C 10 – 20 Min. 200 °C
Layer thickness	5909/5907/5903/591M	60 – 90 µm ISO 2360
Gloss level	5909	> 85, R'/60° ISO 2813/60°
	5907	65 – 85, R'/60°
	5903	25 – 35, R'/60°
	591M	5 – 25, R'/60°

Testing methods	Testing standards	Results
Mechanical values		
Adhesion	ISO 2409, Tape AAMA 2604-05, 7.4.1.1	GT 0
Erichsen cupping	ISO 1520, Tape	> 5 mm
Mandrel bending test	ISO 1519, Tape	< 5 mm
Hemispherical impact test	ASTM D 2794, Tape AAMA 2604-05, 7.5	2.5 Nm
Abrasion test	ASTM D 4060 AAMA 2604-05, 7.6	approx. 40 mg
Mechanical machining	Qualicoat-Test 2.18	With sharpened tools: no tearing or flaking when sawing, milling, drilling etc.
Corrosion tests		
Acetic acid salt-spray test Neutral salt-spray test	ISO 9227 AASS AAMA 2604-05, 7.8.2	After 1000 hours: < 1 mm infiltration, no bubbles
Water condensate exposure test	DIN EN ISO 6270-2 AT ASTM D2247, ASTM D 714 AAMA 2604-05, 7.8.1	After 1000 hours: < 1 mm infiltration, no bubbles
Mortar resistance	ASTM C207c/D3260 AAMA 2604-05, 7.7.2	Can be removed easily and without leaving any residue after 24 hours
Weather-resistance		
Florida test	ISO 2810, 5° S	3 years
Color change		max. 5 ΔE (CIELab)
Loss of gloss		max. 50 %
Chalking resistance		8–10, according ASTM, D4214

Pre-treatment of coated substrate: aluminium sheets, AlMg1 sheet; 0.8 mm

Pre-treatment acc. to DIN 50939 or DIN EN 12487; yellow or green chromatising

Your facade: aesthetic and protected – even after 10 years and more

Exterior facades are exposed every day to the growing influence of the environment and weathering. Safeguarding the aesthetic effect of a stylishly designed architectural property places high demands on the composition of coatings and requires reliable long-term testing. This is where IGP-HWF 3001 sets standards, simultaneously offering the best possible protection and a wide range of design options. The intelligent IGP-DURA[®]*clean* effect reduces dirt adhesion and lowers maintenance costs.

Surface aspects

- Good coverage properties
- Pearl and iron mica effects
- High mortar resistance
- High abrasion-resistance to ASTM D 4060

IGP-DURA[®]*clean* effect

- Easy to clean, with reduced dirt adhesion
- Low maintenance costs
- Value-enhancing surface

IGP safety and tested quality

A complete guarantee chain for the quality powders from the production up to the coating process (certified coaters) is supervised by GSB and Qualicoat for the architectural sector.

The performance results of IGP-HWF 3001 go over and beyond the set requirements.

- Eco-friendly production
- Long-term, object-related guarantee on gloss and color stability according to the regulations of GSB "Master" and/or Qualicoat "Class 2"



Economical

- Very good coverage
- Savings as a result of highly consistent powder recovery, including effect powders

Group Companies

Germany

IGP Pulvertechnik Deutschland GmbH
Dieselstrasse 7, DE-84030 Landshut
Postfach 1565, DE-84003 Landshut
Phone +49 (0)871 7609 430
Fax +49 (0)871 7609 470
verkauf@ig-pulver.de

France

IGP Pulvertechnik Sarl
Bâtiment EUROPA 1 – Site d'Archamps
FR-74160 Archamps
Phone +33 (0)4 50 95 35 10
Fax +33 (0)4 50 95 30 15
ig.poudre@wanadoo.fr

Great Britain

IGP UK
Unit 8, Yate Campus
10 North Rd, Yate
GB-Bristol, BS37 7PA
Phone +44 (0)1454 800 020
Fax +44 (0)1454 318 072
enquiries@igpuk.com

Austria

IGP Pulvertechnik GesmbH
Wienerstrasse 99
AT-2514 Traiskirchen
Phone +43 (0)2252 508046
Fax +43 (0)2252 508046 14
verkauf@igpulver.at

Poland

IGP Pulvertechnik Polska Sp. z o.o.
ul. Łąkowa 3
PL-05-822 Milanówek
Phone +48 (0)22 724 94 49
Phone/Fax +48 (0)22 758 31 83
Fax +48 (0)22 758 37 98
igp@igp.pl
www.igp.pl

Hungary

IGP Hungary Kft.
Kisfaludy u. 6–8
HU-6000 Kecskemét
Phone +36 76 507 974
Fax +36 76 507 975
info@igphungary.hu
www.igphungary.hu

Distribution Partners

Benelux

Intercoatings EB B.V.
Welsommerweg 33
NL-7722 RP Dalfsen
Postbus 43
NL-7720 AA Dalfsen
Phone +31 529 46 94 00
Fax +31 529 46 94 01
info@intercoatings.nl
www.intercoatings.nl

Bulgaria

Ultracoating Ltd
Galileo Galilei Bl. 251 Vh. G
BG-1113 Sofia
Phone +359 2 490 0075
Fax +359 2 870 6349
ultracoating@abv.bg

Estonia

Inlook Color Oü
Valdeku 132
EE-11216 Tallinn
Phone +372 658 57 08
Fax +372 655 92 25
inlook@online.ee

Finland

Inlook OY
Sahaajankatu 1
FI-00880 Helsinki
Phone +358 20 7589 200
Fax +358 20 7589 320
info@inlook.fi

Lithuania

UAB Inlook Vilnius
Lentvario g. 7
LT-02300 Vilnius
Phone +3705 2 640 404
Fax +3705 2 640 402
info@inlook.lt
www.inlook.lt

Romania

S.C. Paint Art S.R.L.
Str. Gorjului nr. 5, sc. C, ap. 26
RO-550063 Sibiu
Phone +40 (0)269 21 49 15
Fax +40 (0)269 21 49 15
office@paintart.ro

Serbia, Bosnia and Herzegovina, Croatia, Montenegro, Macedonia

IGeAL Oberflächentechnik D.O.O
ul. Pere Velimirovića 41
SRB-11000 Belgrad
Phone +381 (0)11 2660 721
Fax +381 (0)11 2661 739
igeal@eunet.yu

Slovenia

PROSET Segovci d.o.o.
Segovci 1b
SI-9253 Apace
Phone +386 2 569 8140
Fax +386 2 569 8141
info@proset.si
www.proset.si

Czech Republic/Slovakia

OK Color spol. s.r.o.
U Pekarky 7
CZ-180 00 Praha 8
Phone +420 283 881 252
Fax +420 286 891 097
praha@okcolor.cz

Belarus

Agrisovgas-Bel
Kuprevich St. 2
BY-220040 Minsk
Phone +375 17 202 99 56
Fax +375 17 202 99 90
igp@telecom.by



Powderful Solutions.

IGP Pulvertechnik AG
Industrie Stelz, Kirchberg
9500 Wil
Switzerland
Phone +41 (0)71 929 81 11
Fax +41 (0)71 929 81 81
www.igp.ch
info@igp.ch

www.doldgroup.com